



BRACELET LNR. 30557 - CU ALLOY - BRONZE AGE - SWITZERLAND

Artefact name Bracelet Lnr. 30557

Authors Sabine. Brechbühl (archaeological service canton Bern, Bern, Bern, Switzerland) & Naima. Gutknecht (HE-Arc CR, Neuchâtel, Neuchâtel,

Switzerland)

Url /artefacts/1096/

▼ The object



Fig. 1: Bracelet,

Credit Archaeological Service Canton Bern.

▼ Description and visual observation

Description of the artefact Round hollow bracelet with lunar section and flat end. The outside face has decorative lines on the outer surface. The inner

Type of artefact Jewellery

Origin Möringen, Biel/Bienne, Bern, Switzerland

Recovering date 2015

Chronology category Bronze Age

chronology tpq

chronology taq

Chronology comment

Burial conditions / environment Lake

Artefact location archaeological service canton Bern, Bern, Bern

Owner archaeological service canton Bern, Bern, Bern

Inv. number Lnr. 30557





Complementary information

White crystals developed after rinsing the object.



Fig. 2: Location of XRF analysis (red circles) and Fig. 3,

Credit Archaeological Service Canton Bern / HE-Arc CR, N.Gutknecht.

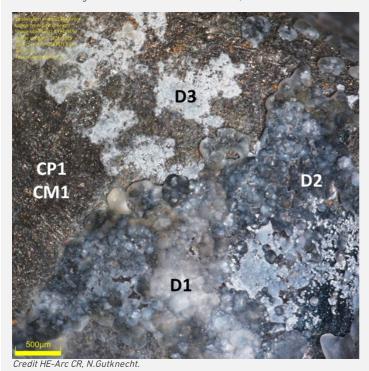


Fig. 3: Detail of the corrosion structure showing the strata documented in Fig. 4,

The schematic representation below gives an overview of the corrosion structure encountered on the bracelet from a first visual macroscopic observation.

Strata	Type of stratum	Principal characteristics	
D1	Deposit	Extra light grey, medium, botryoidal microstructure, scattered, compact, hard	
D2	Deposit	Grey, medium, botryoidal microstructure, scattered, compact, hard	

D3	Deposit	White, thin, drusy aggregate, scattered, compact, soft	
CP1	Corrosion product	Olive green, thin, discontinuous, compact, soft	
CM1	M1 Corroded metal Layer, average ratio (50/50) between CP1 and M1		
M1	Metal	Yellow. metallic, soft, dendrites microstructures	

Table 1: Description of the principal characteristics of the stratum as observed under binocular and described according to Bertholon's method.

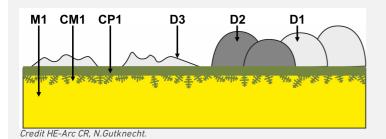


Fig. 4: Stratigraphic representation of the corrosion structure of the bracelet by macroscopic and binocular observation,




Fig. 5: Stratigraphic representation of the corrosion structure of the bracelet observed macroscopically under binocular microscope using the MiCorr application with reference to the whole Fig. 4. The characteristics of the strata are only accessible by clicking on the drawing that redirects you to the search tool by stratigraphy representation, Credit HE-Arc CR, N.Gutknecht.

Description of sample No sample has been taken. The observation and analysis were performed in a non-invasive way on the object.

Alloy Cu Alloy

Technology Cast

Lab number of sample

Sample location None Responsible institution None

Date and aim of sampling

Complementary information

None.

Analyses performed:

Non invasive approach

- XRF with handheld portable X-ray fluorescence spectrometer (NITON XL3t 950 Air GOLDD+, Thermo Fischer®). General Metal mode, acquisition time 60s (filters: Li20/Lo20/M20).
- Raman spectroscopy: it is performed on a Renishaw VIRSA Raman Analyser spectrometer equipped with a 785nm laser, the laser power employed is 1mW with 15 acquisition time of 1s.

The XRF analysis was carried out without sampling. All strata, from soil and corrosion products to metal, are analyzed at the same time. The metal is presumably a copper-tin alloy with some lead, while Si probably originates from the burial environment.

Elements (mass %)	1	σ	2	σ
Cu	81.9	0.5	83.1	0.7
Sn	10.2	0.1	9.8	0.1
Pb	1.9	0.03	1.4	0.03
Si	1.9	0.1	1.7	0.2
Fe	1.5	0.03	1.3	0.03
S	0.2	0.03	/	/

Table 2: Chemical composition of the surface of the bracelet at two representative points shown in Fig. 2. The results are rounded up to 1 number after the comma.

Raman spectroscopy was performed on different surface deposits (D1, D2 and D3). The hypothesis was that it could be a development of corrosion products since it was only observed after drying and storage. Nevertheless, the Raman spectra of the three crystal types (D1/Pt1, D2/Pt2 and D3/Pt3) correspond well to the reference spectra of calcite (Fig. 7). It appears to be a deposit from the burial environment (lake) with different levels of crystallisation.


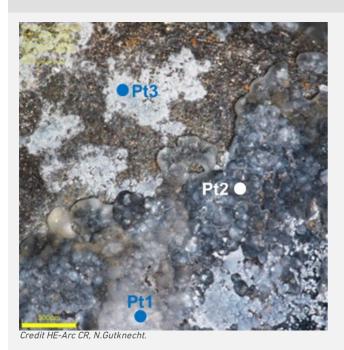


Fig. 6: Location of the Raman analysis,



Credit HE-Arc CR, N.Gutknecht.

Calcite (RRUFF ID: R040070.1

Fig. 7: Raman spectra reference for calcite (RRUFF ID=R040070.1) and points 1, 2 $\,$ and 3 located in Fig. 6,

The composition of the metal is assessed from XRF in table 2: it should be a leaded bronze.					
Microstructure	Dendritic structure				
First metal element	Cu				
Other metal elements	Sn, Pb				
Complementary information					
Complementary information None.					
None.					
★ Corrosion layers					
CP1 (data not shown) was matched with cuprite (CuO ₂) through Raman spectroscopy.					
Corrosion form	None				
Corrosion type	None				
Complementary information					
None.					
▼ Synthesis of the binocular / cross-sectio	n examination of the corrosion structure				
Synthesis of the binocutal 7 cross-section	n examination of the corresion structure				
None.					
★ Conclusion					
The bracelet is a tin bronze probably with s from the lake burial condition.	some lead. It appears to be covered with copper oxide (cuprite) and various types of crystals attributed to calcite				
As this object comes from a lake environm	ent, it was expected that a lake patina (copper iron sulphide - chalcopyrite) would be found and that the white				
products would be a sulphate deterioration of the chalcopyrite. However, the description of the corrosion structure does not correspond to any of the lake patinas documented in Schweizer's publication (Schweizer, 1994) or in the MiCorr database. We can therefore exclude the hypothesis of deterioration of the					
lake patina from observation alone. The white crystals are deposits from the lake environment and were present prior to the drying of the object, but were only documented afterwards.					
▼ References					
1. Schweizer, F. (1994) Bronze objects from Lake sites: from patina to bibliography. In: Ancient and historic metals, conservation and scientific research (eds. Scott, D.A., Podany, J. and Considine B.B.), The Getty Conservation Institute, 33–50.					