

# BUGATTI 37 CYLINDER HEAD GASKET 0416 – AL ALLOY – MODERN TIMES – FRANCE

**Artefact name** Bugatti 37 cylinder head gasket 0416

**Authors** Christian. Degrigny (HE-Arc CR, Neuchâtel, Neuchâtel, Switzerland) & Elodie. Granget (HE-Arc CR, Neuchâtel, Neuchâtel, Switzerland) & Brice. Chalançon (MNAM (Musée National de l'Automobile de Mulhouse), Mulhouse, Alsace, France)

**Url** /artefacts/1124/


## ∨ The object



Credit He-Arc CR, E.Granget.

Fig. 1: General picture of the corroded cylinder head gasket of the Bugatti Type 37. Top side facing the camshaft and bottom part in contact with the coolant of the block,

Fig. 2: Gasket located in red on technical drawing of the engine from Cresswell,

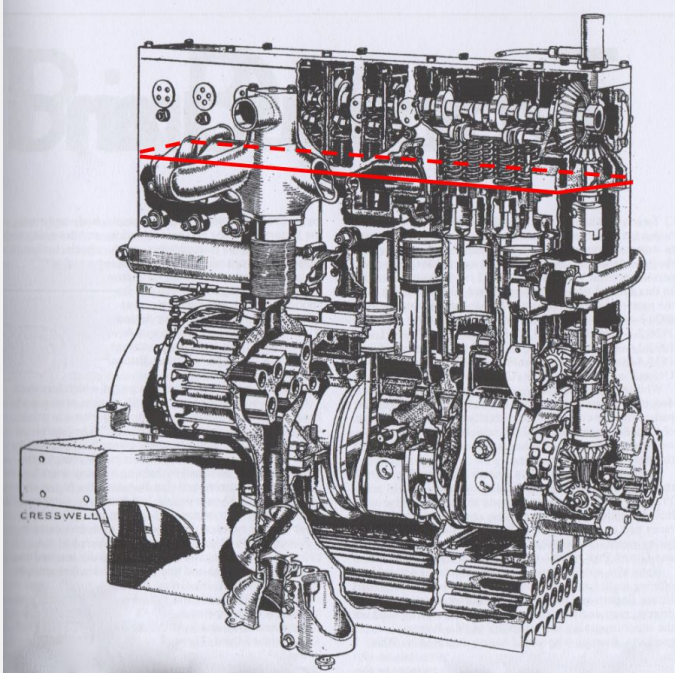

Credit He-Arc CR, E.Granget.

## ∨ Description and visual observation

<b>Description of the artefact</b>	A coolant flows through the cylinder block inside galleries. This aluminium gasket is making a tight junction between the camshaft and the top of the block (Fig. 2). It keeps the water or coolant (water + glycol-based antifreeze) from mixing with the lubricant used on the shaft, the pistons and the cylinders. The wet side is facing the cylinder block. The other side is dry.
<b>Type of artefact</b>	Technical object
<b>Origin</b>	MNAM (Musée National de l'Automobile de Mulhouse), Mulhouse, Alsace, France
<b>Recovering date</b>	Unknown
<b>Chronology category</b>	Modern Times
<b>chronology tpq</b>	<input type="text" value="1926"/> A.D. ▾
<b>chronology taq</b>	<input type="text" value=""/> ---- ▾
<b>Chronology comment</b>	The production of this model started in 1926
<b>Burial conditions / environment</b>	Outdoor to indoor atmosphere
<b>Artefact location</b>	MNAM (Musée National de l'Automobile de Mulhouse), Mulhouse, Alsace
<b>Owner</b>	MNAM (Musée National de l'Automobile de Mulhouse), Mulhouse, Alsace
<b>Inv. number</b>	0416
<b>Recorded conservation data</b>	Vehicule kept functional until 2008 - dismantlement in 2018

## Complementary information


A combustion engine transforms thermal energy into kinetic energy. In the Bugatti Type 37, this engine has 3 parts:

- The camshaft case above, where the camshaft coordinates the pistons.
- The cylinder block in the middle, where the cylinders slide in a linear motion.
- The crankcase block below, where the crankshaft transforms the motion from linear to rotative.

The explosion and the cylinders movement are generating a lot of heat. Therefore, the block needs to be cooled down. A cooling system circulates water or coolant between the block [hot] and a heat exchanger (or radiator) [cold]. The circulation of the liquid is often supported by a water pump. The coolant flows through the block inside galleries in order to cool down the cylinders without wetting them. (Poulain, 1995, p.86)

The Bugatti Type 37 will be restored. When the car was dismantled, this gasket was deemed too corroded to be kept. A new part will be put in its place during the restoration. Consequently, this part has been classified as study material, allowing for sampling for metallography.

Study area(s)

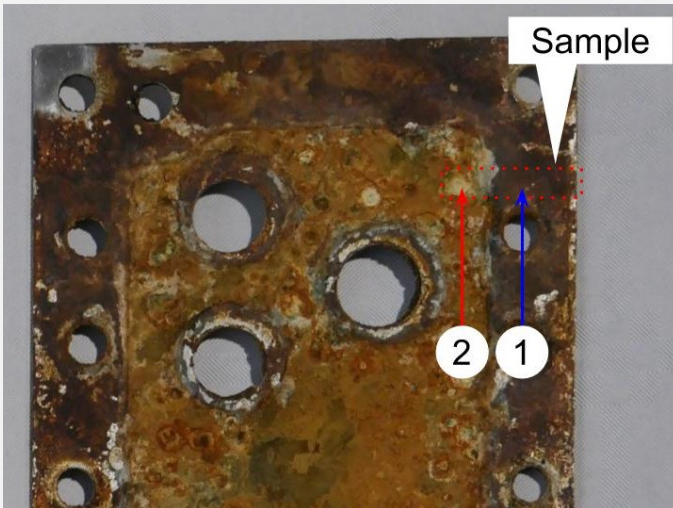

Credit He-Arc CR, E.Granget.

Fig. 3: Bugatti Type 37 cylinder head gasket. Location of the sampling area (red rectangle). Stratigraphic observation sites, in contact with the block [1] and in contact with the coolant [2],


Binocular observation and representation of the corrosion structure

Fig.3 clearly shows the limit where the gasket is in contact with the cylinder block ([1] edges and circular openings in the center) and where it is in contact with the coolant ([2] center).

The schematic representation below gives an overview of the corrosion layers encountered on these areas (Fig. 4). The metal core (M1) is colonated on both sides with metal M2.

Stratigraphy [1]	Stratigraphy [2]
The metal contains the strata M1 and M2.	The first metal stratum is missing and only the core metal (M2 in strat.[1], now M1) remains.
The CP1 is a thin brown layer loosely attached to the surface of M1. It can be removed with a firm brush.	The CP1 is a thick bright orange layer, really powdery and easily detached. It can be partly removed with a firm brush. The coloration is less important closer to the metal interface, where the products are white. This layer is also really fragile and friable.
In some places, CP2 develops within M1. It is colored in bright orange and can be broken in pieces with a toothpick.	The CP2 is peaking through CP1 in some places, colored in green.


Fig. 4: Stratigraphic representation of corrosion zones in contact with the block [1] and in contact with the coolant [2],

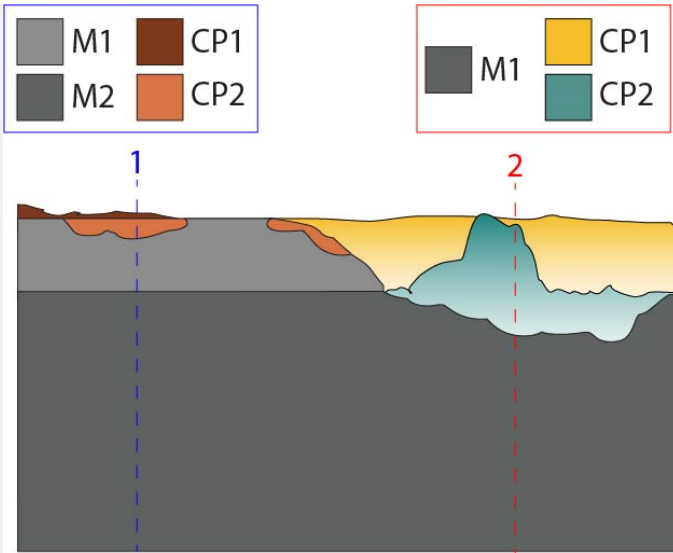

Credit HE-Arc CR, E.Granget.

∨ MiCorr stratigraphy(ies) – Bi

∨ Sample(s)

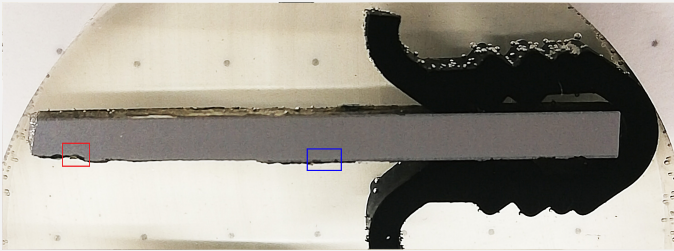

Credit HE-Arc CR, E.Granget.

Fig. 5: Micrograph of the cross-section sampled from the Bugatti T37 gasket showing the location of zone 1 in blue (Fig. 6) and zone 2 in red (Fig. 8),

#### Description of sample

The sample shown on Fig.5 is a transversal cut of the gasket presenting 3 different corrosion sites.

Bottom side:

Contact with coolant [1].

Contact with block [2].

Top side:

Contact with oil (not presented in this artefact sheet).

#### Alloy

Al Alloy

#### Technology

Rolled (probably hot rolling) and annealed

#### Lab number of sample

None

#### Sample location

HE-Arc CR, Neuchâtel, Neuchâtel

#### Responsible institution

MNAM (Musée National de l'Automobile de Mulhouse), Mulhouse, Alsace

#### Date and aim of sampling

31.12.2019 - Sampled for Metallography

## Complementary information

During sampling, a large part of the top corrosion layer (CP1) was lost for both zones 1 and 2.

### ∨ Analyses and results

#### *Analyses performed on the gasket:*

XRF with portable X-ray fluorescence spectrometer (Niton XL3t 950 Air Gold+ analyser Thermo Fischer (voltage 50V, General metals mode with acquisition times 20s (main) / 20s (Low) /20s (Light).

#### *Analyses performed on the cross-section sampled from the gasket, on the bottom side (contact with the coolant [1] and with the block [2]):*

Metallography (unetched), BF and DF imaging; SEM-EDS (20kV): SE and BSE imaging and semi-quantitative EDS analysis.

### ∨ Non invasive analysis

None.

### ∨ Metal

This gasket is made out of two metals colaminated: an Al-Cu alloy core (M2 in Fig. 4, Table 1) with on each side a pure Al sheet (M1 in Fig. 4, Table 2).

Element	mass %
Al	94
Cu	3.8
Mg	2
Mn	0.7
Si	0.1

Table 1: Chemical composition (mass %) of the metal (core) of the gasket. Method of analysis: SEM-EDS, HEI-Arc, S.Ramseyer.


Element	mass %
Al	99.6
Fe	0.3
Si	<0.1

Table 2: Chemical composition (mass %) of the metal (colaminated protective sheet) of the gasket. Method of analysis: SEM-EDS, HEI-Arc, S.Ramseyer.

Fig. 7 shows oriented inclusions on both M1 and M2, as well as a lot of small pores in M2.


Local analyses on each phase appearing on Fig. 7 showed that the roll-bounded metal M1 is a compact (non-porous) sheet of pure Al (Table 1) with oriented inclusions of Fe and Si. The core M2 is a very porous alloy composed of Al with bigger oriented inclusions of Si, Mn, Fe, Mg.

Fig. 6: Micrograph of the cross-section of the gasket, zone 1, shown on Fig. 5 unetched, dark field, showing the location of the EDS elemental chemical distribution of Fig. 10 to 13 (in blue) and of the SEM image of Fig. 7 (in red),

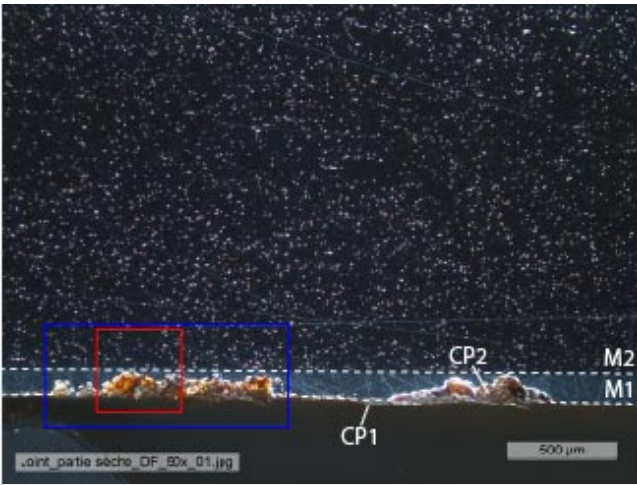

Credit HEI Arc, S.Ramseyer / Edit: He-Arc CR, E.Granget.

Fig 7: SEM detail (BSE mode) of zone 1 of the colaminated sheet in cross-section. The core metal (M2) is porous (in black) and shows oriented inclusions (in white) and the colaminated metal (M1) is compact and has smaller oriented inclusions (in white). Corrosion products (in dark grey) are limited to M1,

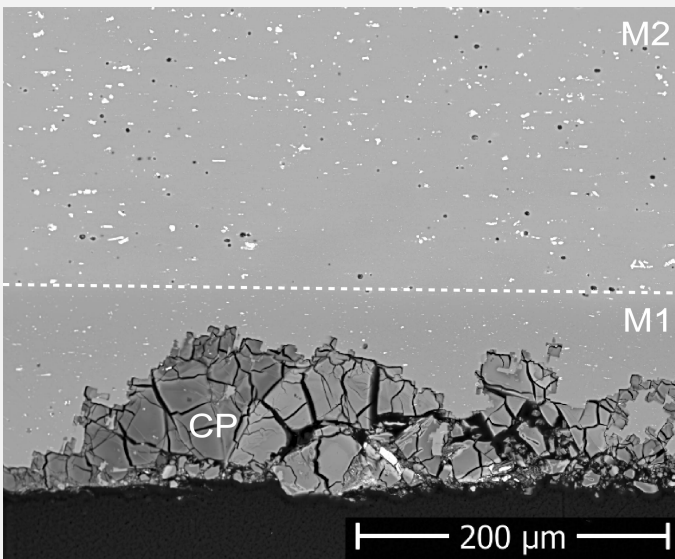

Credit HEI Arc, S.Ramseyer / Edit: He-Arc CR, E.Granget.

Microstructure	Unknown
First metal element	Al
Other metal elements	Mg, Si, Mn, Fe, Cu


#### Complementary information

None.


#### Corrosion layers

Fig. 7 shows that the corrosion products progress through M1 and develop a network of cracks. Fig. 8 shows that the corrosion can expand even further through M2 (zone 2), the corrosion products being more stratified (Fig. 9). The EDS elemental chemical distribution of zone 1 is given in Fig. 11 to 13. The corrosion layers contain S (probably aluminium sulfate (Fig. 12), polluted with Fe (Fig. 11)). The presence of sulfur can be explained by the proximity of the gasket to the combustion chamber. As for the iron, it is probably coming from the steel block.


Fig. 8: Micrograph of the cross-section of the gasket, zone 2, shown on Fig. 5 unetched, dark field, showing the location of

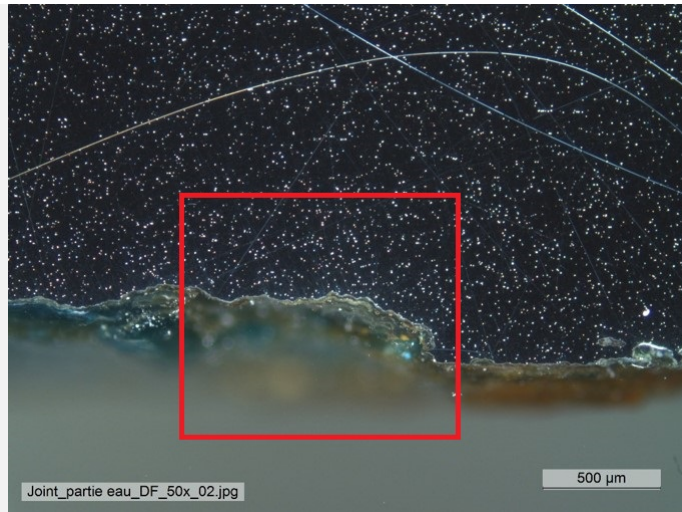


Credit HEI Arc, S.Ramseyer / Edit: He-Arc CR, E.Granget.

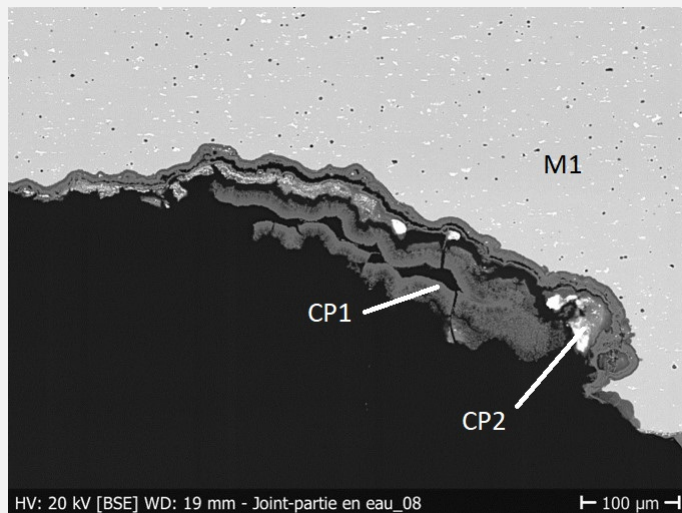

Credit HEI Arc, S.Ramseyer / Edit: He-Arc CR, E.Granget.

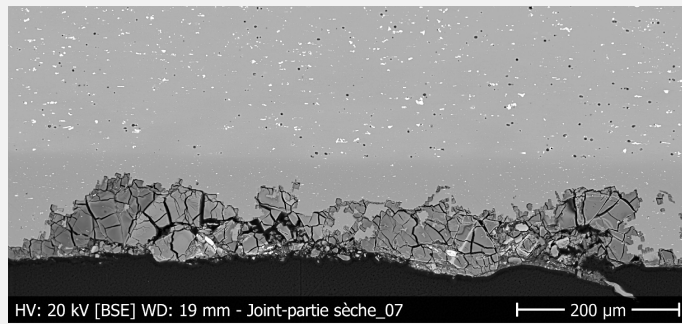

Credit HEI Arc, S.Ramseyer.

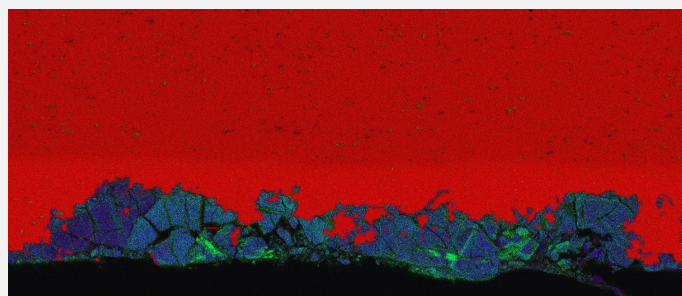

Credit HEI Arc, S.Ramseyer.


the SEM image of Fig. 9 (in red),

Fig 9: SEM detail (BSE mode) of zone 2 of the gasket in cross-section. The colaminated Al is missing. The core metal (now M1) is porous (black spots) and shows oriented inclusions (in white). The corrosion products (CP1) are very friable and retain clusters of inclusions that are also corroded (CP2),


Fig. 10: SEM image (BSE mode) of the cross-section of zone 2 of the gasket (detail of Fig. 6) showing the core metal on top (M2) and the heavily corroded colaminated metal (M1),

Fig. 11: Al (red), O (blue) and Fe (green) chemical distribution of the area of Fig. 10. Method of analysis: SEM-EDS. Lab. of Electronic Microscopy and Microanalysis, Néode, HEI Arc.

Fig. 12: S chemical distribution of the area of Fig. 10. Method of analysis: SEM-EDS. Lab. of Electronic Microscopy and Microanalysis, Néode, HEI Arc.

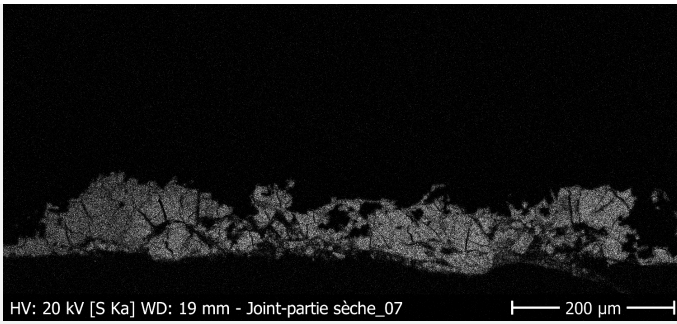

Credit HEI Arc, S.Ramseyer.

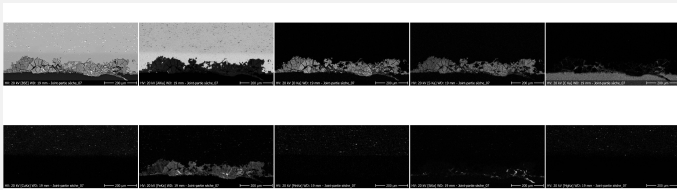

Credit HEI Arc, S.Ramseyer.

Fig. 13: SEM image and elemental chemical distribution of the area of Fig. 10. Method of analysis: SEM-EDS. Lab. of Electronic Microscopy and Microanalysis, Néode, HEI Arc.

<b>Corrosion form</b>	Multiform
<b>Corrosion type</b>	?

**Complementary information**

None.

∨ MiCorr stratigraphy(ies) – CS

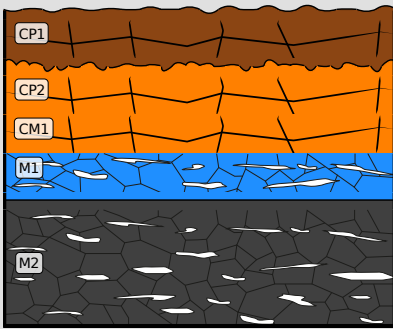


Fig. 14: Stratigraphic representation of the gasket (zone 1) in cross-section (dark field), using the MiCorr application. The characteristics of the strata are only accessible by clicking on the drawing that redirects you to the search tool by stratigraphy representation. This representation can be compared to Fig. 7, Credit HE-Arc CR, E.Granget.

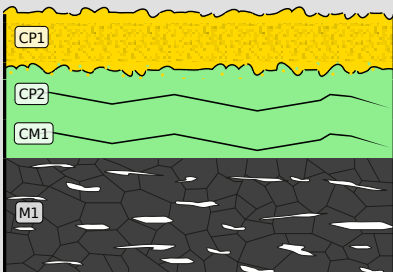


Fig. 15: Stratigraphic representation of the gasket (zone 2) in cross-section (dark field), using the MiCorr application. The characteristics of the strata are only accessible by clicking on the drawing that redirects you to the search tool by stratigraphy representation. This representation can be compared to Fig. 9, Credit HE-Arc CR, E.Granget.

∨ Synthesis of the binocular / cross-section examination of the corrosion structure

The schematic representations of corrosion layers of Figs. 6 and 7 integrating additional information based on the analyses carried out is given in Fig. 16.



No analyses could be carried out on the top thicker part of CP1.

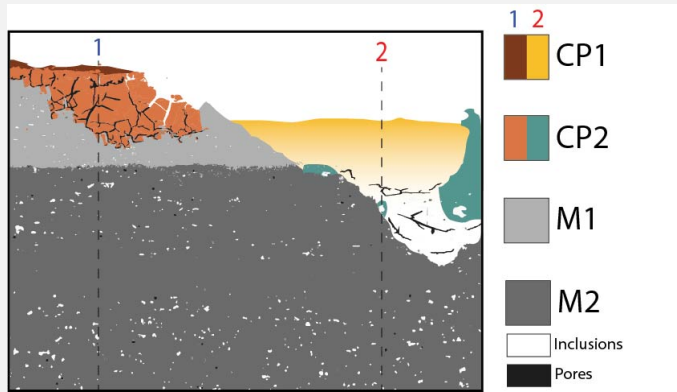


Fig. 16: Improved stratigraphic representation of the 2 corrosion structures of the Bugatti cylinder head gasket. CP1 could not be analysed,

Credit He-Arc CR, E.Granget.

## Conclusion

The cylinder head gasket of this Bugatti Type 37 is made of colaminated aluminium alloys. A pure aluminium sheet (with traces of Fe and Si) protects an Al-Cu core alloy (Al, Cu, Mg, Mn, Si) on both sides of the gasket. The gasket seals the upper part of the cylinder block, preventing coolant from flowing to the camshaft or cylinders.

The side of the gasket facing the cylinder block has a different corrosion pattern depending on whether the area is immersed or not. The surface in contact with the cylinder block shows a priori corrosion consisting of highly cracked aluminium sulphate (network). The surface immersed in the coolant is heavily corroded. The colaminated Al sheet has been completely consumed, and the corrosion progresses through the support metal, retaining inclusions of the alloy in its products. This layer is very brittle and tends to delaminate.

All the corrosion products are contaminated with iron oxides, probably from the block. The immersed part is covered with a thick crust of what is believed to be a mixture of ferrous and aluminium-based products.

## References

### References on object and sample

#### References object

1. Poulain, P. and J-M. (1995) *Voitures de collection : Restauration Mécanique Editions Techniques pour l'Automobile et l'Industrie (ETAI), Paris.*
2. Granget, E. (2020) *La corrosion des alliages d'aluminium des circuits de refroidissement à eau de véhicules en contexte patrimonial : Utilisation d'outils open-access dans l'établissement d'un diagnostic des altérations d'un corpus de véhicules conservés au Musée National de l'Automobile de Mulhouse (Collection Schlumpf), Rapport interne MNAM.*

#### References sample

3. Granget, E. (2020) *La corrosion des alliages d'aluminium des circuits de refroidissement à eau de véhicules en contexte patrimonial : Utilisation d'outils open-access dans l'établissement d'un diagnostic des altérations d'un corpus de véhicules conservés au Musée National de l'Automobile de Mulhouse (Collection Schlumpf), Rapport interne MNAM.*

### References on analytic methods and interpretation

4. Vargel, C. (2004) *Corrosion of Aluminium, Elsevier.*
5. Degryny C. and Schröter J. (2019) *Aluminium Alloys in Swiss Public Collections: Identification and Development of Diagnostic Tools to Assess Their Condition, in METAL 2019, proceedings of the ICOM-CC Metal WG interim meeting, eds. C. Chemello, L. Brambilla, E. Joseph, Neuchâtel (Switzerland), 408-415.*

