



DEFORMED FRAGMENT OF METAL SHEET WT10-M305 - TIN BRONZE - IRON AGE - SWITZERLAND

Artefact name Deformed fragment of metal sheet WT10-M305

Authors Marianne. Senn (EMPA, Dübendorf, Zurich, Switzerland) & Christian. Degrigny (HE-Arc CR, Neuchâtel, Neuchâtel, Switzerland)

Url /artefacts/1216/

▼ The object




Fig. 1: Deformed fragment of metal sheet (section and front side) (after Department of Prehistory, University of Zurich),

▼ Description and visual observation

Description of the artefact

Deformed fragment of metal sheet with a dark green and grey powdery surface (patina) that might have been caused by

exposure to high temperatures (Fig. 1). A green layer appears below the dark surface. Dimensions: L = 2.4cm; W = 2.3cm;

WT = 4.8g.

Type of artefact Metal sheet

Origin Ritual place Wartau Ochsenberg, Sankt Gallen, Saint Gallen, Switzerland

Recovering date Excavation in 1991

Chronology category Iron Age

chronology tpq 500 B.C. ▶

chronology taq 401 B.C. ▶

Chronology comment 5th Century BC

Burial conditions / environment Soil

Artefact location Kantonsarchäologie, Sankt Gallen, Saint Gallen

Owner Kantonsarchäologie, Sankt Gallen, Saint Gallen

Inv. number WT10-M305


Recorded conservation data Not conserved

Complementary information

None.

Study area(s)

Fig. 2: Location of sampling area,



Credit HE-Arc CR.

▼ Binocular observation and representation of the corrosion structure

None.

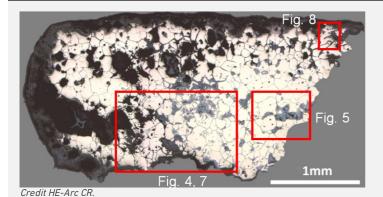


Fig. 3: Micrograph of the cross-section of the sample (Fig. 2) taken from the deformed fragment of metal sheet with dark green / grey patina showing the location of Figs. 4, 5, 7 and 8, unetched, bright field,

Description of sample

The sample is a section from the top right corner of the sheet (Fig. 2). Its dimensions are: L=2.5mm and W=2.3mm. The metal is surrounded on three sides by corrosion products. Intergranular corrosion has developed throughout the metal

section (Fig. 3).

Alloy Tin Bronze

Technology Secondary recrystallization (produced by burning) after cold working

Lab number of sample MAH 92-5-2-003

Sample location Musées d'art et d'histoire, Genève, Geneva

Responsible institution Musées d'art et d'histoire, Genève, Geneva

Date and aim of sampling 1992, examination of the corrosion layer

Complementary information

None.

Analyses performed:

 $Metallography\ (etched\ with\ ferric\ chloride\ reagent),\ Vickers\ hardness\ testing,\ ICP-OES,\ SEM/EDS,\ Raman\ spectroscopy.$

None.

The remaining metal is a porous (red arrows on Fig. 4) tin bronze (Table 1). Five analyses were carried out. S was detected in the non-corroded part of the metal (2 measurements) while P was present only in the corroded metal (3 measurements). As no major difference in the composition was observed (comparison of relative standard deviation, RSD) all analyses were used to calculate the median value. Inter- and transgranular corrosion has developed so extensively that all grain boundaries and twin lines are outlined (Fig. 4). After etching, the metal shows annealed polygonal grains with a few twins and slip lines below the surface (Fig. 5). The slip lines are restricted to the right side of the sample where the metal is best preserved (Fig. 4). The grain size varies between 50 and 170µm, due to an excessively long or hot annealing procedure leading to a grain coarsening. Small copper sulphide inclusions appear in blue (Fig. 4). The average hardness of the metal is HV1 90.

Elements	Cu	Sn	As			Со		Pb	Sb	Ag	Zn	Fe	Bi
mass% (median value of 5 measurements)	83.13	16	0.26	0.1	0.07	0.032	0.025	0.02	0.02	0.009	0.002	<	0.002
RSD %	2	9	13	25	45	3	5	41	15	12	6	<	43

Table 1: Chemical composition of the metal. Analytical method: LA-ICP-MS, Laboratory of Basic Aspects of Analytical Chemistry at the Faculty of Chemistry, University of Warsaw, PL. *S is only present in the metal, whereas **P indicates the presence of corrosion products in the analysed metal.

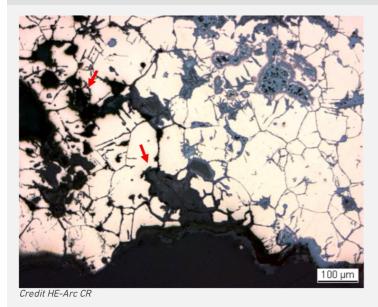


Fig. 4: Micrograph of the metal sample from Fig. 3 (detail), unetched, bright field. Extensive inter- and transgranular corrosion has developed within the metal. Possible large pores are visible (arrows) inside the remaining metal,

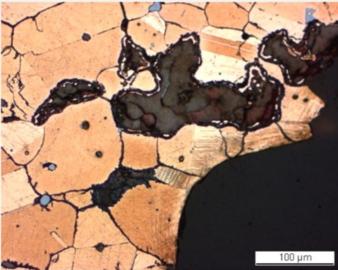


Fig. 5: Micrograph of the metal sample from Fig. 3 (detail), etched, bright field. We observe pink-orange polygonal grains with twins and slip lines as well as copper sulphide inclusions (in blue),

Credit HE-Arc CR.

Microstructure Large polygonal grains with few twins + strain lines

First metal element Cu

Other metal elements As, Sn

Complementary information


None.

♥ Corrosion Lavers

The corrosion crust varies in thickness between 60 and 150µm (Fig. 3). In bright field, it appears dark-grey (Fig. 4) and consists of two layers (CP1 and CP2). The inner layer is dark-grey and dense while the thin outer layer is slightly lighter coloured. Within the metal, the corrosion products are light-grey (CP3, Fig. 4). Under polarized light, the corrosion layer turns blue-green with dark-blue areas (Figs. 6 and 7) whereas corrosion products inside the metal are either light-blue or red-orange (Figs. 6 and 7). The red corrosion products (CP3) have the composition of cuprite/Cu20 while the orange compounds (also CP3) are enriched in Sn (Table 2). The blue-green corrosion products (CP2) both within the remaining metal and on the surface are even richer in Sn and 0, and contain some P (Table 2 and Fig. 8). The thin, irregular dark-grey surface layer (CP1) is enriched in P, Fe, Si and Al (Table 2 and Fig. 8). XRD analyses of powdery particles sampled from the thin, dark surface corrosion layer (CP1) indicate the presence of tenorite/Cu0 and cassiterite/Sn02 (Museum report 1992). The Raman spectra of this layer (Fig. 9) confirmed the presence of tenorite.

			Sn		Fe		As	Total
CP1, outer dark-grey corrosion layer. Fig 7		16	49	<	3	3	1	106
CP2, blue-green middle corrosion layer. Fig. 7		21	41	1	<	2	<1	106
CP3, Red corrosion product (average of 2 similar analyses). Fig. 7		95	<	<	<	<	<	106
CP3, Orange corrosion product (average of 2 similar analyses). Fig. 7		54	30	<1	<	<	<1	109
Blue-green corrosion product. Fig. 8		21	51	1	<	<	1	106
Blue-green inner corrosion layer. Fig. 8		22	39	1	<	1	<	97


Table 2: Chemical composition (mass %, <: below the detection limit) of the different corrosion products and layers from Figs. 6 and 7. Method of analysis: SEM/EDS, Laboratory of Analytical Chemistry, Empa.

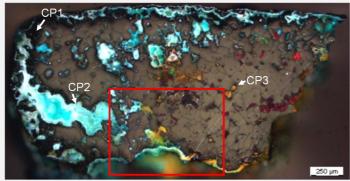

Credit HE-Arc CR.

Fig. 6: Micrograph of the cross-section of the metal sample (same as Fig. 3) and corresponding to the stratigraphy of Fig. 10, polarised light, showing the location of Fig. 7,

Fig. 7: Micrograph of the metal sample (same as Fig. 4), polarised light. In black the metal. Blue-green, orange and red corrosion products are found in the porous metal and along the grain boundaries,

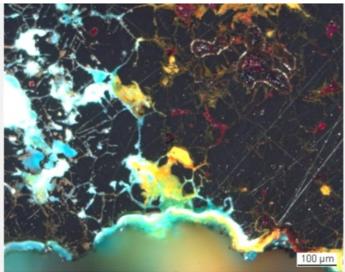

Credit HE-Arc CR.

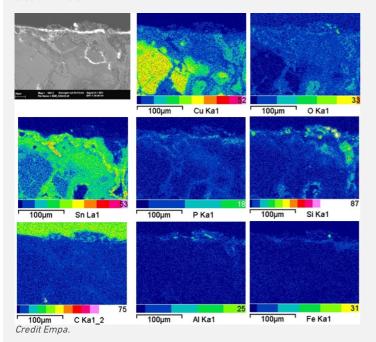


Fig. 8: SEM image, SE-mode, and elemental chemical distribution of the selected area from Fig. 3. Method of examination: SEM/EDS, Laboratory of Analytical Chemistry, Empa,

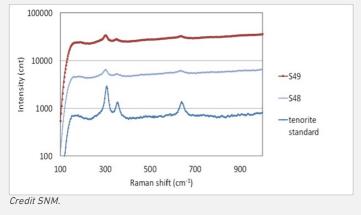


Fig. 9: Raman spectra of the outer dark corrosion layer (S48 and S49) compared to a tenorite standard spectrum. Settings: laser wavelength 532nm, acquisition time 20s for S48 and 100s for S49, one accumulation, filter D1 (7.5-8mW), hole 500, slit 80, grating 600. Method of analysis: Raman spectroscopy, Lab of Swiss National Museum, Affoltern a. Albis ZH,

Corrosion form

Uniform - intergranular

Corrosion type

Mostly type II with locally type I (Robbiola)

Complementary information

None.

MiCorr stratigraphy(ies) – CS

Fig. 10: Stratigraphic representation of the sample taken from the deformed fragment of metal sheet with dark green / grey patina in cross-section (dark field) using the MiCorr application. The characteristics of the strata are only accessible by clicking on the drawing that redirects you to the search tool by stratigraphy representation. This representation can be compared to Fig. 6, Credit HE-Arc CR.

imes Synthesis of the binocular / cross-section examination of the corrosion structure

Corrected stratigraphic representation: none.

▼ Conclusion

The tin bronze sheet shows traces of cold working but has been exposed to an extended or excessively hot annealing process. According to Northover (Northover in preparation), the relative lack of twins and their large size confirm a prolonged annealing process. Furthermore large grains, large twins and extensive intergranular corrosion are characteristic of objects that have been exposed to a hot reducing flame either in a house fire or on a funeral pyre. All corrosion products except the cuprite are Sn enriched. The enrichment in P of the surface layer might be due to an environment rich in organic material (for example bones). Tenorite analysed by XRD and Raman spectroscopy is very rare in ancient Cu corrosion and must be interpreted as a further tracer for Cu corrosion in burning context. The original surface of the metal has been destroyed resulting in a type 2 corrosion layer after Robbiola et al. 1998. Only locally in the areas where tenorite is preserved does type 1 patina occur.

▼ References

References on object and sample

Reference object

1. Publication in preparation (Biljana Schmid-Sikimic).

Reference sample

- 2. Degli Agosti, M., Santoro, I., Senn, M., Untersuchungen zur Brandpatina an Kupferlegierungen. In: Schmid-Sikimic, B. in preparation.
- 3. Northover, P. Untersuchungen an Fragmenten einiger Negauer-Helme. In Schmid-Sikimic, B. in preparation.
- 4. Rapport d'examen (1992) Laboratoire Musées d'art et d'histoire, Genève 92-5-2.

References on analytic methods and interpretation

5. Robbiola, L., Blengino, J-M., Fiaud, C. (1998) Morphology and mechanisms of formation of natural patinas on archaeological Cu-Sn alloys, Corrosion Science, 40, 12, 2083-2111.