

# ARMATURE FROM A CLOCK MOVEMENT MIH IV-212 - ZN AL SN CU ALLOY - MODERN TIMES - SWITZERLAND

<b>Artefact name</b>	Armature from a clock movement MIH IV-212
<b>Authors</b>	Marianne. Senn (Empa, Dübendorf, Zurich, Switzerland) & Christian. Degriigny (HE-Arc CR, Neuchâtel, Neuchâtel, Switzerland)
<b>Url</b>	/artefacts/1576/

## ∨ The object



Fig. 1: Broken armature (left) from the clock movement of a wooden wall clock (right) (after Seematter 2009),

Credit HE-Arc CR.

## ∨ Description and visual observation

<b>Description of the artefact</b>	Armature from the clock movement of a wooden wall clock with electric movement, broken in two elements (Fig. 1 and Fig. 2) with a heavily cracked surface.
<b>Type of artefact</b>	Horological object
<b>Origin</b>	Wooden wall clock, La Chaux-de-Fonds, Neuchâtel, Switzerland
<b>Recovering date</b>	1902-1904
<b>Chronology category</b>	Modern Times
<b>chronology tpq</b>	<input type="text" value="1902"/> A.D. ▾
<b>chronology taq</b>	<input type="text" value="1904"/> A.D. ▾
<b>Chronology comment</b>	

<b>Burial conditions / environment</b>	Indoor atmosphere
<b>Artefact location</b>	International museum of horology (IMH), La Chaux-de-Fonds, Neuchâtel
<b>Owner</b>	International museum of horology (IMH), La Chaux-de-Fonds, Neuchâtel
<b>Inv. number</b>	MIH IV-212
<b>Recorded conservation data</b>	N/A

**Complementary information**

None.

∨ Study area(s)



Credit HE-Arc CR.

Fig. 2: Location of sampling area on one of the two broken elements of the armature,

∨ Binocular observation and representation of the corrosion structure

None.

∨ MiCorr stratigraphy(ies) – Bi

∨ Sample(s)

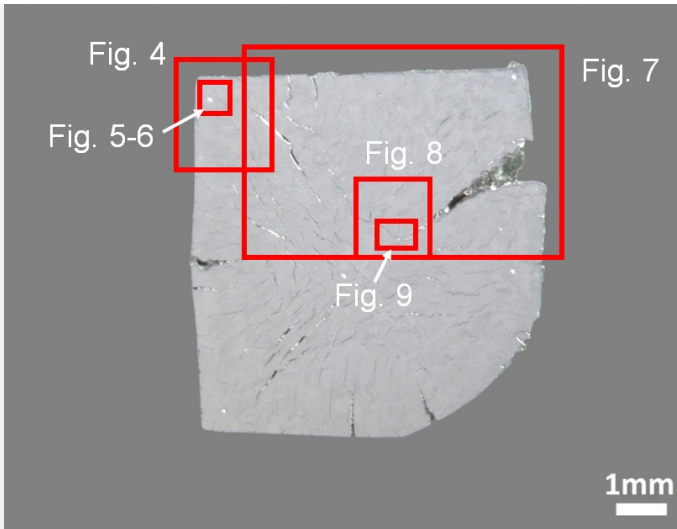


Fig. 3: Micrograph of the cross-section of the fragment sampled from the armature showing the location of Figs. 4 to 9,

Credit HE-Arc CR.

<b>Description of sample</b>	This sample is the complete cross-section from one of the two broken elements of the armature (Fig. 2). The metal has large cracks radiating from the centre to the outside which have deformed the armature (Fig. 3).
<b>Alloy</b>	Zn Al Sn Cu Alloy
<b>Technology</b>	As-cast
<b>Lab number of sample</b>	MIH-VI-212
<b>Sample location</b>	HE-Arc CR, Neuchâtel, Neuchâtel
<b>Responsible institution</b>	International museum of horology (IMH), La Chaux-de-Fonds, Neuchâtel
<b>Date and aim of sampling</b>	2009, metal analysis

**Complementary information**

The metal is covered with a Ni coating.

∨ **Analyses and results**

**Analyses performed:**  
Metallography (unetched), Vickers hardness testing, SEM/EDS.


∨ **Non invasive analysis**

None.

The metal is a Zn-Al-Sn-Cu alloy (Table 1) with an average hardness of HV1 105. A fine dendritic structure is observed (Fig. 4) which consists of clearly separated Zn, Al-Cu and Sn-rich phases (Figs. 5 and 6). Pb is associated with Sn but also forms tiny nodules.


Elements	Zn	Al	Sn	Cu	Pb	Total
Metal	67	17	11	4	<1	99

Table 1: Chemical composition (mass %) of the metal (oxygen not shown). Method of analysis: SEM/EDS, Lab of Electronic Microscopy and microanalysis, IMA (Néode), HEI Arc.

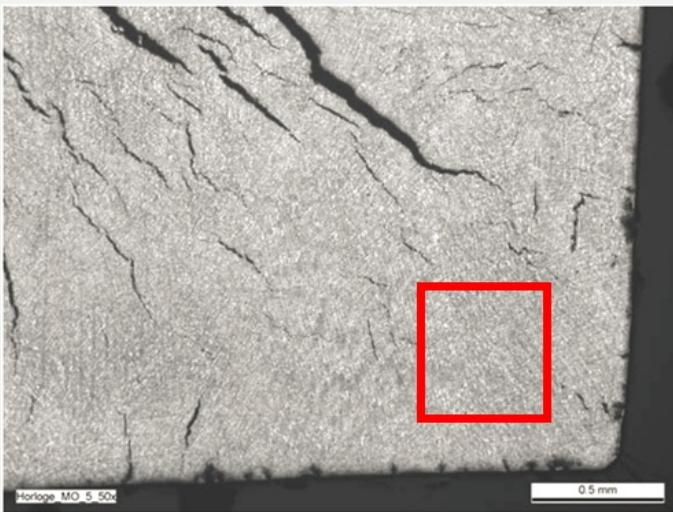

Credit HE-Arc CR.

Fig. 4: Micrograph of the metal sample from Fig. 3 (inverted picture, rotated by 270°, detail), unetched, bright field. A dendritic structure is visible. The micrograph of Fig. 5 is marked by a square,

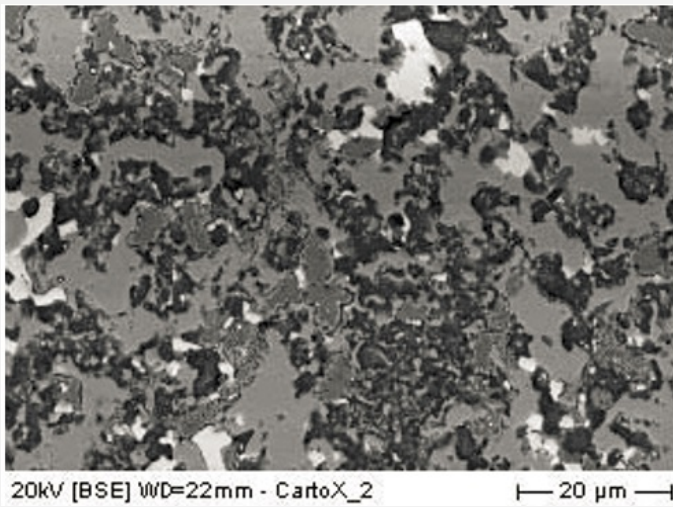

Credit HE-Arc CR.

Fig. 5: SEM image, BSE-mode, detail from Fig. 4 (detail), unetched, bright field. Three phases appear: in light-grey the Zn-rich phase, in dark-grey the Al and Cu-rich phase and in white the Sn-rich phase,

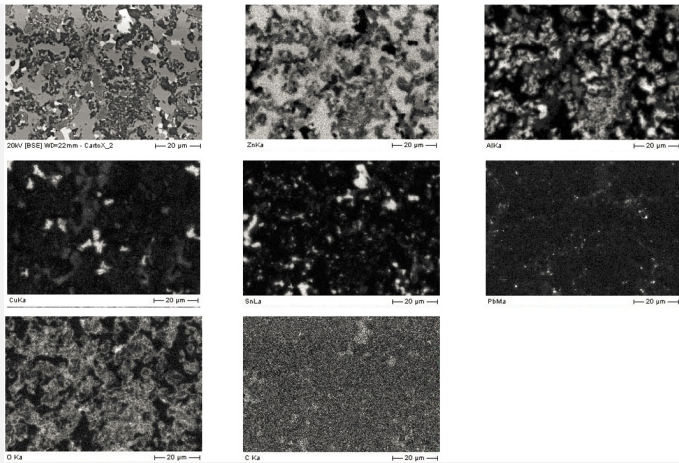


Fig. 6: SEM image, BSE-mode, and elemental chemical distribution of the selected area from Fig. 5. Method of examination: SEM/EDS, Lab of Electronic Microscopy and microanalysis, IMA (Néode), HEI Arc,

Credit HE-Arc CR.


<b>Microstructure</b>	Fine dendritic structure (no cohesion between the phases)
<b>First metal element</b>	Zn
<b>Other metal elements</b>	Cu, Sn, Al

#### Complementary information

None.


#### Corrosion layers

The Zn-rich phase is heavily oxidised internally (Fig. 6). The corrosion has developed throughout the entire metal body, generating cracks (Figs. 7 and 8). The cracks are Zn, O and C-rich (Fig. 9) and could be composed of zinc carbonate.

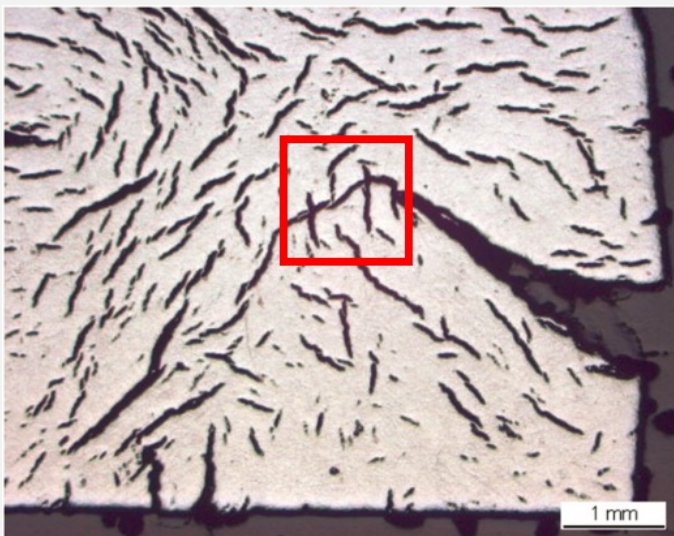


Credit HE-Arc CR.

Fig. 7: Micrograph showing the metal - "corrosion products" interface from Fig. 3 (reversed picture, detail), unetched, bright field,

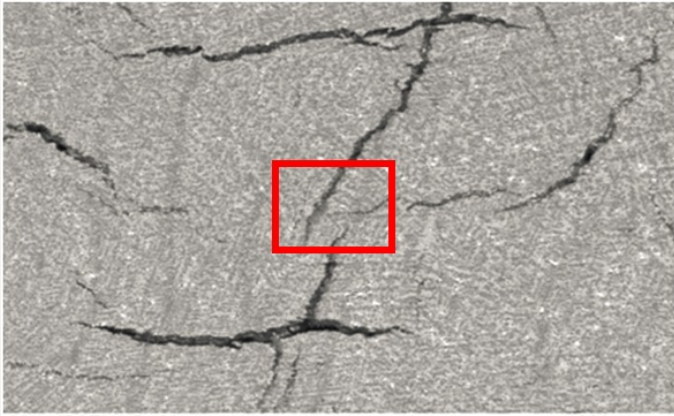

20kV [BSE] WD=22mm - Horloge\_zone cartoX\_1\_1  
Credit HE-Arc CR.

Fig. 8: Micrograph of the metal sample, detail from Fig. 7 (reversed and rotated by 90°), unetched, bright field. A dendritic structure is visible. The area selected for elementary mapping (Fig. 9) is marked by a rectangle. Can be compared to the stratigraphy representation of Fig. 10,

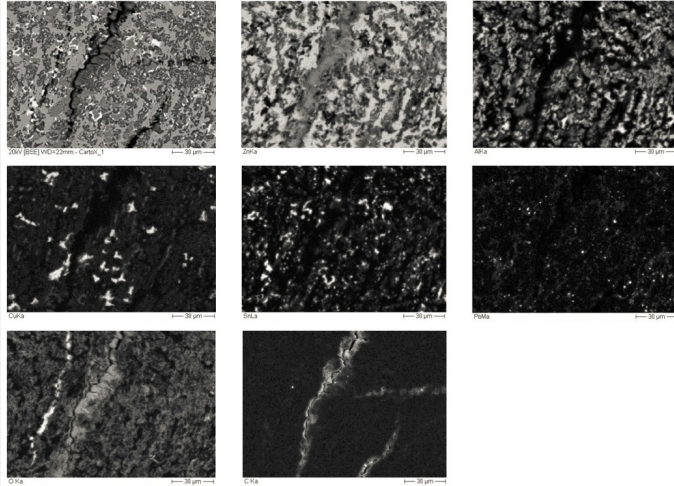

Credit HE-Arc CR.

Fig. 9: SEM image, BSE-mode, and elemental chemical distribution of the selected area from Fig. 8 (detail). Method of examination: SEM/EDX, Lab of Electronic Microscopy and microanalysis, IMA (Néode), HEI Arc,

**Corrosion form** Internal cracking  
**Corrosion type** zinc pest

**Complementary information**

None.

✓ MiCorr stratigraphy(ies) – CS

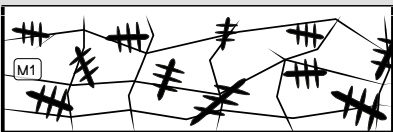


Fig. 10: Stratigraphic representation of the fragment sampled from the armature in cross-section (dark field) using the MiCorr application. The characteristics of the stratum are only accessible by clicking on the drawing that redirects you to the search tool by stratigraphy representation. This representation can be compared to Fig. 8, Credit HE-Arc CR.

✓ Synthesis of the binocular / cross-section examination of the corrosion structure

None.

## ∨ Conclusion

The armature of the clock mechanism is constituted of a ZnAlSnCu alloy. The absence of cohesion between the different phases has led to the penetration of O during the manufacturing of the alloy. Small original cracks have developed further eventually causing the armature to break. This phenomenon is called zinc pest. It develops mainly on cast objects, starting with localised modifications (blisters and pits, Cramer and Covino 2005).

It appears that the armature was made of an unsuccessful experimental alloy. The IMH has in its collection a similar mechanism with the same armature but made of an another more stable alloy, suggesting then that our armature was some kind of prototype element.

## ∨ References

### References on object and sample

#### *References object*

1. Seemater, V. (2009) Conservation-restauration d'une horloge à mouvement électrique, rapport interne HE Arc CR.

#### *References sample*

2. Seemater, V. (2009) Conservation-restauration d'une horloge à mouvement électrique, rapport interne HE Arc CR.

### References on analytic methods and interpretation

3. Cramer, S.D., Covino Jr., B.S. volume editors. (2005). ASM Handbook, 13B, 37.