SACRIFICIAL ANODE VHS-8339 - ZN ALLOY - MODERN TIMES

Artefact name	Sacrificial anode VHS-8339
Authors	Marianne. Senn (EMPA, Dübendorf, Zurich, Switzerland) & Christian. Degrigny (HE-Arc CR, Neuchâtel, Neuchâtel, Switzerland)
Url	/artefacts/218/

The object





Credit HE-Arc CR.

Fig. 1: Submarine and the anode (www.verkehrshaus.ch),

Description and visual observation


Description of the artefact	Half of possibly a weight or sacrificial anode. It is surrounded by a whitish brown-grey corrosion crust, the broken metal has a greyish shining colour, whereas the cut metal part is silvery. Dimensions: L = 4.9cm ; WT = 95g.
Type of artefact	Submarine part
Origin	Submarine "Mesoscaph" from Auguste Piccard
Recovering date	The sacrificial anodes (?) might have been added when the submarine was used in the sea.
Chronology category	Modern Times
chronology tpq	1970 A.D.
chronology taq	1974 A.D.
Chronology comment	1970 _ 1974
Burial conditions / environment	Outdoor atmosphere
Artefact location	Swiss Museum of Transport, Luzern, Lucerne
Owner	Swiss Museum of Transport, Luzern, Lucerne
Inv. number	VHS-8339
Recorded conservation data	Not conserved

Complementary information

This work is licensed under CC BY-NC-ND 4.0

The anodes were produced by Horton Maritime.

Study area(s)

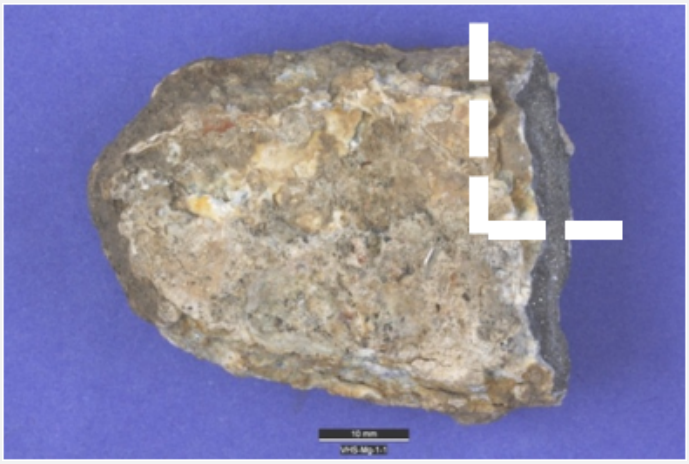

Credit HE-Arc CR.


Fig. 2: Location of sampling area,

Binocular observation and representation of the corrosion structure

Stratigraphic representation: none

MiCorr stratigraphy(ies) – Bi

Sample(s)

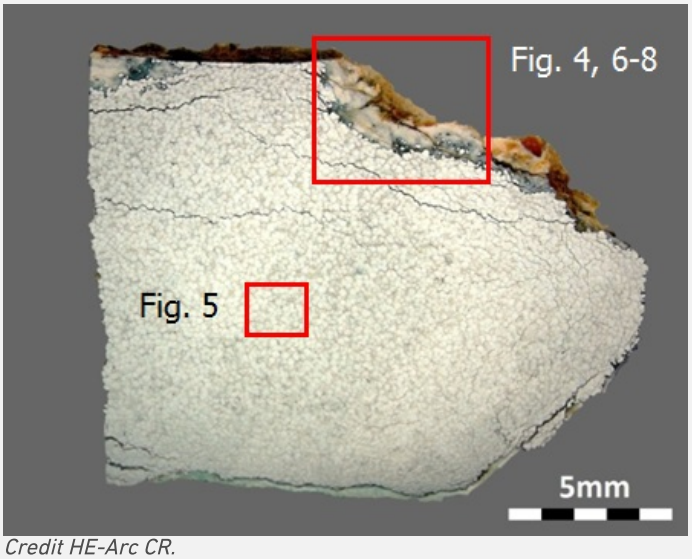

Credit HE-Arc CR.

Fig. 3: Micrograph of the cross-section showing the locations of Figures 4 to 8,

Description of sample

The sample shows a cross-section from the sacrificial anode. The thickness of the corrosion crust is variable. Dimensions: L = 17mm; W = 14mm.

This work is licensed under CC BY-NC-ND 4.0

Alloy	Zn Alloy
Technology	Cast and annealed
Lab number of sample	VHS-Mq-1
Sample location	Empa (Marianne Senn)
Responsible institution	Swiss Museum of Transport, Luzern, Lucerne
Date and aim of sampling	07/09/2009 metallography

Analyses and results

Analyses performed:
Metallography (unetched), Vickers hardness testing, SEM/EDX.


Non invasive analysis

Metal

The remaining metal is an almost pure zinc alloy (Table 1). The oxygen content is not from the original alloy, but is due to secondary corrosion. The metal grains are visible without etching and present a polygonal structure (Figs. 4 and 5). The structure is recrystallised after annealing. The recrystallization of zinc alloys begins at room temperature.

Elements	Zn	Al	O	Total
Metal	95	0.8	1.6	97

Table 1: Chemical composition (mass %) of the metal. Method of analysis: SEM/EDX, Lab Analytical Chemistry, Empa.

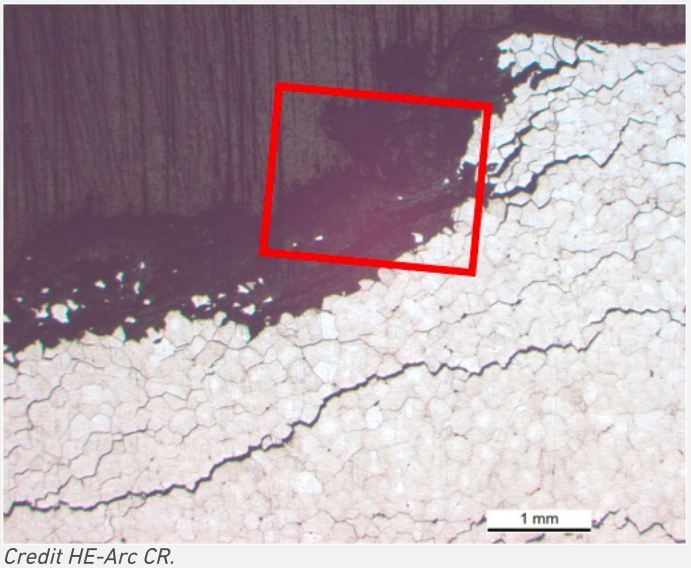

Credit HE-Arc CR.

Fig. 4: Micrograph of the metal sample from Fig. 3 (reversed picture, detail), unetched, bright field. Extensive intergranular corrosion is visible.The rectangle marks Fig. 6,

This work is licensed under CC BY-NC-ND 4.0

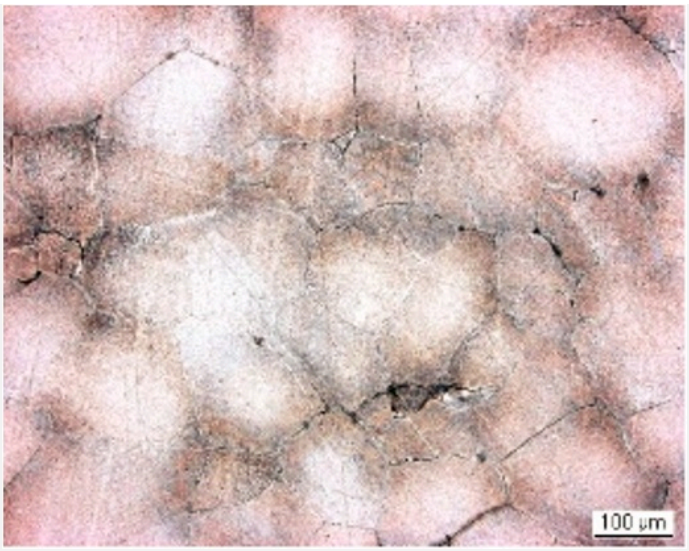


Fig. 5: Micrograph of the metal sample from Fig. 3 (detail), etched,

Credit HE-Arc CR.

Microstructure	Recrystallized structure (polygonal grains)
First metal element	Zn
Other metal elements	


Corrosion layers

Extended intergranular corrosion has developed in the metal structure (Figs. 4, 5 & 6). The metal is covered by a corrosion crust that is hard to see in bright field and which contains remnant metal (Fig. 5). On most of the sample the corrosion crust is uniform. In areas we see cracks appearing as brown lines separating the corrosion crust (Figs. 6 and 7). In bright field the corrosion crust appears grey containing dark-grey zones (Fig. 6). Under polarized light, the corrosion crust appears white with darker parts including remnant metal (Fig. 7). It contains Zn and O as well as S along some cracks (Fig. 9). The cracks appear in brown.

Elements	O	Al	Zn	Total
Light-grey corrosion part	23	<	77	98
Dark grey corrosion part	38	0.6	68	106


Table 2. Chemical composition (mass %) of the corrosion layer from Fig. 6. Method of analysis: SEM/EDX, Laboratory of Analytical Chemistry, Empa.

This work is licensed under CC BY-NC-ND 4.0

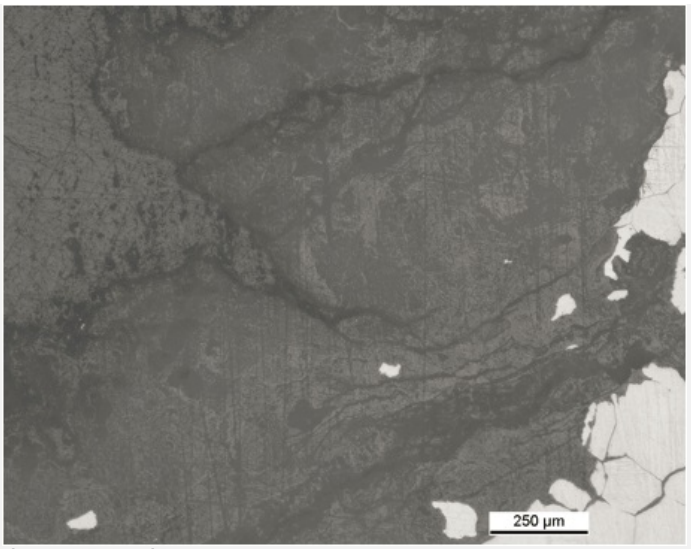


Credit HE-Arc CR.

Fig. 6: Micrograph showing the metal - corrosion products interface from Fig. 4 (detail), unetched, bright field,

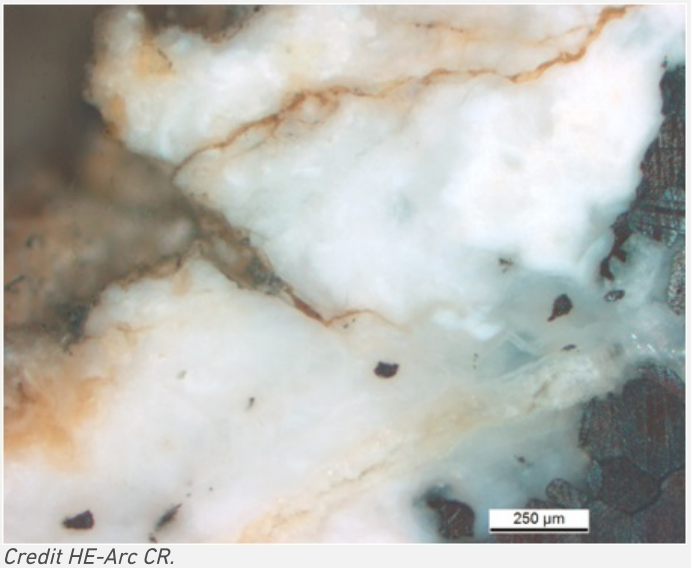

Credit HE-Arc CR.

Fig. 7: Micrograph (same as Fig. 6), unetched, polarised light. We observe in dark-grey the metal, in white the corrosion crust separated by brown cracks including remnant metal,

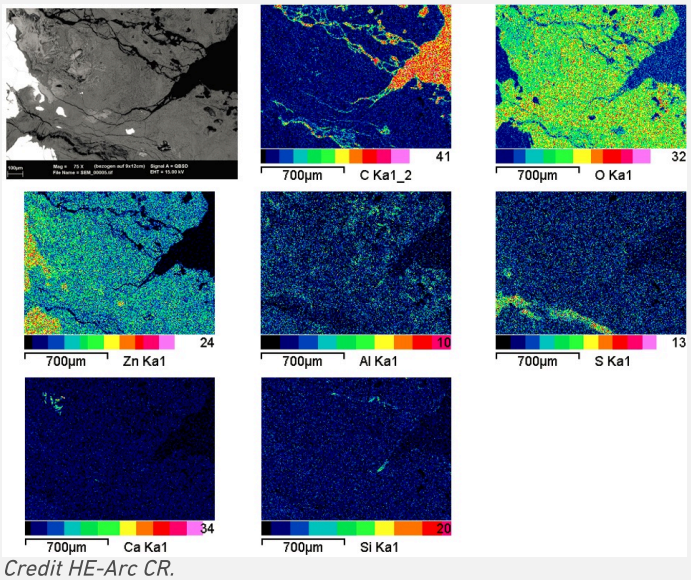

Credit HE-Arc CR.

Fig. 8: SEM image, BSD-mode, and elemental chemical distribution of most of the area of Fig. 6 (reversed picture). Method of examination: SEM/EDX, Laboratory of Analytical Chemistry, Empa,

Corrosion form	Uniform - intergranular
Corrosion type	?

This work is licensed under CC BY-NC-ND 4.0

MiCorr stratigraphy(ies) – CS



Fig. 4: Stratigraphic representation of the object in cross-section using the MiCorr application. This representation can be compared to Fig. 8.

Synthesis of the binocular / cross-section examination of the corrosion structure

Corrected stratigraphic representation: none

Conclusion

The artefact is possibly either a weight or a sacrificial anode. However, it is made of a cast and annealed zinc alloy which makes the interpretation as a weight implausible. In contrast an interpretation as a sacrificial anode is more likely. It is known that zinc alloy sacrificial anodes are used to protect marine propellers especially in salt water. The thick corrosion layer seems to consist of oxides or hydroxides. The origin of the sulphur along some of the cracks is unclear.

References

References on object and sample

References object

1. Auskunftsblatt der Sammlung des Verkehrshauses der Schweiz, Inventarnummer VHS-8339.

References sample

2. MIFAC-métal cat. 29.

References on analytic methods and interpretation

This work is licensed under CC BY-NC-ND 4.0